

Laser versus bur and dentinal bonding

Authors Dr Barbara Cvikl, Dr Alexander Franz, Dr Christoph Kurzmann & Dr Andreas Moritz, Austria

_Introduction

In times of increased awareness of aesthetics, high quality ceramic restorations in dentistry are in great demand. Furthermore, demands for alternative dental preparation techniques like laser preparation which affords non-contacting and vibration-free working, increased. Therefore, laser research and laser application became more and more important in dentistry. However, constantly new developments and this concentrated flow of information can occasionally be a problem for the attending dentist, because it is hardly possible in clinical everyday life to review all new products and information that are given by manufacturers. The purpose of the present work is therefore to provide information about the stability of the adhesive compound between human dentin and ceramic using different laser and conventional preparation tools.

Erbium-based lasers are approved devices for cavity preparation in dentistry.¹⁻⁴ Er:YAG laser and Er,Cr:YSGG laser, hard tissue laser with a wavelength of 2,940 nm and 2,780 nm, respectively, offer a high

surface effect with only a low depth effect on teeth. Due to the large proportion of water in carious tissue, caries will be removed particularly well. An auxiliary bactericidal effect exists. Furthermore the pulpal increase in temperature is not higher than 2,5°C through an efficient water cooling system.⁵⁻⁸ According to a study by Zach et al., temperature increases of less than 6,1°C are considered to be inoffensive for the dental pulp.⁹ All of those elements and other factors like patient-friendly treatment by a vibration-free and contactless preparation technique make Erbium-based lasers the ideal alternative to conventional preparation techniques.¹ Some researchers even suggest that additional acid etching before the adhesive ceramic fixation may not be necessary because of micro roughness, which is achieved by laser treatment.^{6,10,11} In contrast, studies by Bahillo et al.,¹² Lee et al.¹³ and others^{14,15} advice additionally acid etching after laser treatment. Hence, there are still doubts about how laser-treated dentin can bond to adhesive systems. For this reason, we investigated both laser preparation with and without phosphoric acid etching.

As ceramic samples, Cerec®-blocks (MITABLOCS Mark II®), conventional feldspar ceramic were used. We used these CEREC®-blocs because the industrial sintering process under vacuum at 1,170 °C, which can be reproduced at any time, ensures a more homogeneous microstructure with consistent material quality compared to laboratory sintered and lab-processed ceramic restorations. We were thus able to minimize interference factors from the ceramic that otherwise may influence our study results.¹⁶ As adhesive material for gluing the dentin discs on the ceramic blocks we used Variolink® II plus Syntac® (Ivoclar Vivadent,

Fig. 1 Bernhard Gottlieb University Clinic of Dentistry, Medical University of Vienna, Austria



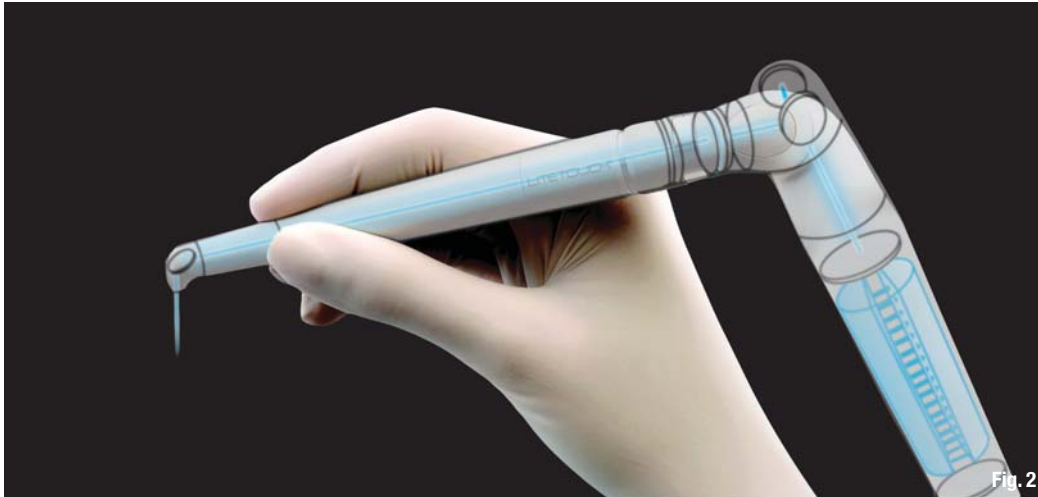


Fig. 2 LiteTouch™ Laser-in-the-Handpiece™: The laser energy is swiftly delivered to the tissue, providing supreme cutting power and precise incisions for hard tissue and bone.

Schaan/Liechtenstein), a classic etch and rinse adhesive system which acts very often as a gold standard.

Materials and Methods

Extracted third molars were cleaned and stored in physiological saline solution. Using a precision saw, cusps were removed and teeth were cut into uniform dentine discs of a thickness of 1 mm. After removal of enamel, dentine discs were randomly divided into five subgroups representing five different preparation techniques: (i) diamond bur and acid etching; (ii) Er:YAG laser (LiteTouch™, Syneron), 2,940 nm, 4 W, 20 Hz; tip of 0,8 mm; (iii) Er:YAG laser and additional acid etching; (iv) Er,Cr:YSGG laser (Waterlase MD™, Biolase), 2,780 nm, 2 W, 30 Hz with a conical tip of 600 μm (MC 6 Saphir); (v) Er,Cr:YSGG laser and additional acid etching. All laser irradiation settings were executed at an angle of inclination of 30° and with a feed rate of 1 mm per minute.

After treatment, dentine discs were fixed on CEREC® ceramic blocks using the system Syntac®/Variolink® II (Syntac® etch & rinse adhesive and Variolink® II, Ivoclar Vivadent, Schaan, Liechtenstein). The system Syntac®/Variolink® II was applied according to the manufacturer's instructions. In addition, the application of human dentin discs on CEREC® ceramic blocks was performed following the manufacturer's instructions.

Sample size of each of the five subgroups was $n = 15$, resulting in a total of 75 dentine discs and 75 CEREC® ceramic blocks. All samples were subjected to thermocycling (10,000 cycles, 5°–55° respectively) to simulate artificial aging. After thermocycling, a shear test was performed using the universal testing machine Zwick (Zwick/Roell, Ulm, Germany) at a crosshead speed of 0.8 mm per minute. The bond strength was registered in megapascals (MPa). Data were analysed using ANOVA with Tukey's post hoc test with a significance level of $\alpha = 0.05$.

Results

The results of the shear bond strength tests showed the highest values for the group of the Er:YAG laser with and without additionally acid etching. The diamond bur and acid etching group as well as the Er,Cr:YSGG laser group with and without additionally acid etching showed similar but slightly lower values (Fig. 1 and Tab. 1). Overall, there was a trend towards stronger bonding with the Er:YAG-laser treated dentin with additionally acid etching; however, no statistically significant differences were exposed when comparing the five preparation methods ($p = 0.169$). These findings suggest that laser irradiation provides favourable conditions for bonding between dentin and ceramics.

Discussion

The results of this study suggest that a laser-treated dentin surface provides favourable conditions for bonding. Our findings that laser treatment can provide coequal adhesive conditions to the diamond bur

Fig. 3 Class V – Cavity Preparation using LiteTouch™. (Courtesy of Dr Avi Reyhanian)



Fig. 3

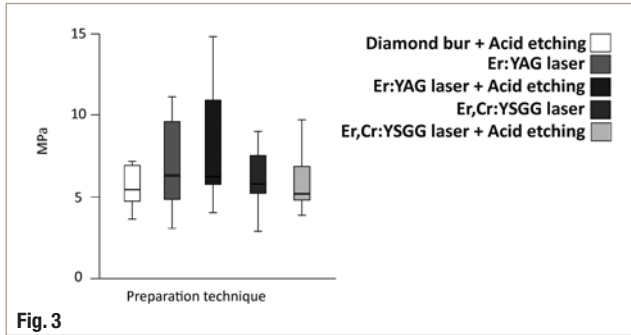


Fig. 3

more, the thickness and especially the size of the dentin discs are of crucial importance, because the bond strength is significantly influenced by the size of the discs.²⁶ Another important factor of the achieved bond strength is the storage medium in which the extracted molars have been stored pending further processing. While we used physiological saline solution to imitate the natural situation as well as possible, other studies applied distilled water, 0,5% chloroform solution and other storage solutions.^{27,28}

Fig. 4_ Comparison of the five preparation techniques with regard to the bonding strength.

	Diamond bur + Acid etching	Er:YAG laser	Er:YAG laser + Acid etching	Er,Cr:YSGG laser	Er,Cr:YSGG laser + Acid etching
Variolink®II	6.84	6.89	8.11	6.11	5.85
Syntac®	+/-3.38	+/-2.7	+/-3.18	+/-1.65	+/-1.67

Table 1_ Means and standard deviations of shear bond strength tests (MPa)

are not supported by the majority of similar studies. In comparable studies using human dentin laser treatment resulted in equivalent¹⁷ or even lower¹⁸⁻²⁰ bond strength to ceramic or composite. However, these studies differed in other experimental aspects (e.g., the laser setting, angle of irradiation, storage conditions for the tooth samples, and the source and preparation of tooth discs).

An explanation for the advantageous results in the laser group could be that we used a standardised process of laser treatment with a constant feed rate and irradiation angle of 30 degrees to the dentin surface. We already obtained promising results with this setting in preliminary tests. We suggest that the superficial part of the laser-irradiated surface is not affected and there are no micro fractures as described in studies with other laser settings.^{14, 21, 22}

In this study we show that Er:YAG-laser treated dentin discs with and without additional acid etching revealed slightly higher mean values than Er,Cr:YSGG laser or bur-treated dentin discs. However, no statistically significant differences were exposed when comparing the different preparation methods. Differences between the results of this study and other studies, which seemed to be comparable at first sight, can be based on a small number of divergences in the study design. A very important factor is the quality and nature of the used adhesive materials and of the dentin discs.

While we used caries-free and mature third molars for the preparation of the dentin discs, other studies applied retained molars, teeth other than molars or enamel surfaces to compare laser preparation with conventional preparation techniques.²³⁻²⁵ Further-

Our findings have to be interpreted with care because *in vitro* settings only partially reflect the *in vivo* performance. Further studies are necessary to understand if these *in vitro* findings translate into clinical practice. Moreover, the *in vitro* system may not necessarily represent the *in vivo* conditions, in which the temperature and humidity are closer to the physiological situation than in our room temperature setting. Other experimental conditions, such as bonding in a climatic chamber and simulation of mastication cycles or long-term storage, can change the bonding strength. Future studies need to consider these physiological situations. There is still room for maximising the bonding strength of dentin to ceramics by improving the laser protocols for the preparation of dental cavities.

Conclusion

Taken together, our findings show that dentin surfaces prepared with the Erbium laser can provide a favourable dentin surface for binding ceramics, particularly when using Variolink®II/Syntac® as the adhesive system. Overall, Erbium laser can be an attractive alternative to the conventional preparation technique using a diamond bur.

_contact	laser
<p>Dr Barbara Cviki Division of Conservative Dentistry; BGZMK, Medical University of Vienna Vienna, Austria</p> <p>barbara.cviki@meduniwien.ac.at</p>	



Tribune CME

Clinical Masters Program in Aesthetic and Restorative Dentistry

10-14 January 2013 and 24-27 April 2013 in Dubai, for a total 9 days

Dubai, UAE

2 on location sessions with **live patient treatment**
and **hands on** in each session!
+ online live and recorded lectures, **online mentoring**



Didier Dietschi



Francesco Mangani



Panos Bazos

Session I: 10 - 14 January 2013 (5 days)

- Direct/Indirect composite Artistry in the Anterior Segment
- Direct/Indirect composite Artistry in the Posterior Segment
- Photography and shade analysis

Clinical Masters:

Didier Dietschi, Francesco Mangani, Panos Bazos



Mauro Fradeani



Urs Brodbeck

Session II: 24 - 27 April 2013 (4 days)


- Full coverage Anterior/Posterior Restoration
- Partial coverage Anterior/Posterior Restoration, Ceramic Restoration

Clinical Masters:

Mauro Fradeani, Urs Brodbeck

ADA C.E.R.P.® | Continuing Education
Recognition Program

Tribune America LLC is the ADA CERP provider.
ADA CERP is a service of the American Dental Association to assist dental professionals in identifying quality providers of continuing dental education. ADA CERP does not approve or endorse individual courses or instructors, nor does it imply acceptance of credit hours by boards of dentistry.

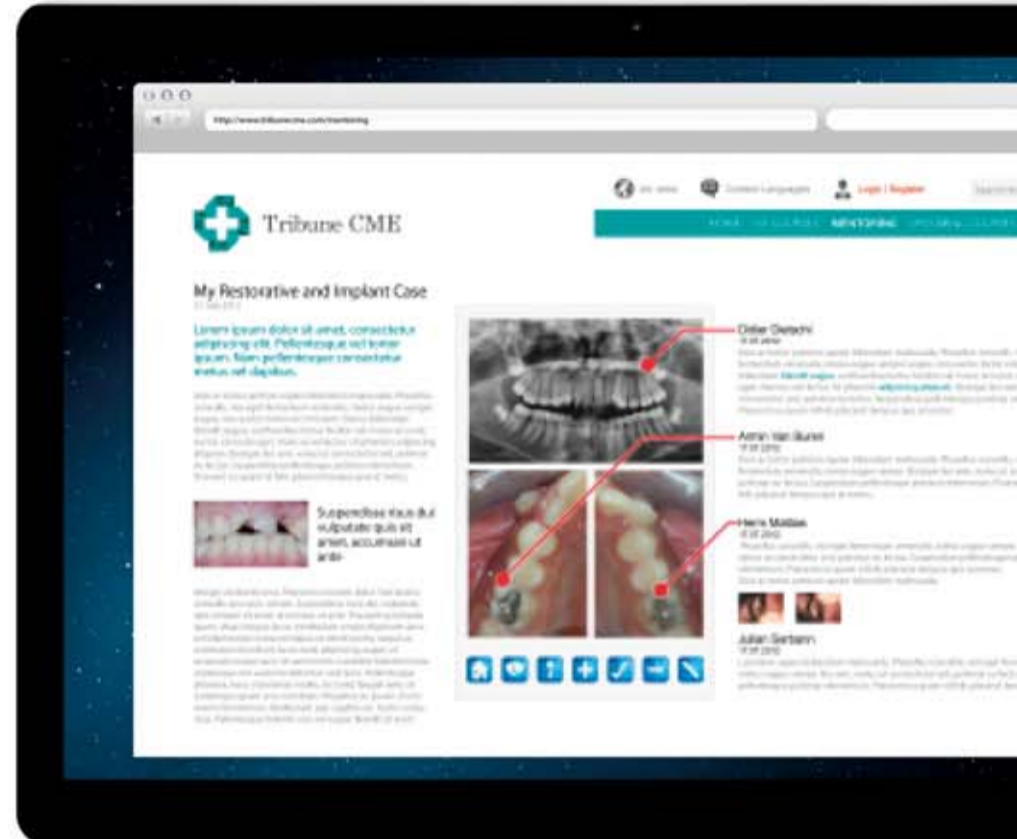

Full access to our online learning platform:
hours of premium video training and live webinars
collaborate with peers and faculty on **your cases**

Registration info

Course fee: € 8,900

Register by the end of October and you
will receive a complimentary iPad
preloaded with premium dental courses

Tribune CME

Tel.: +49-341-48474-302

email: info@tribunecme.com

www.TribuneCME.com



Discover the Master's secrets and Dubai's superlatives



100

C.E. CREDITS

ADA CERP® | Continuing Education
Recognition Program

